

# Geopolymerization of Mining Tailings as an Alternative for Its Use in the Construction Industry

**C. Toledo**

Pontifical Catholic University of Peru, Lima, Peru

**M. Guzman**

Pontifical Catholic University of Peru, Lima, Peru

**J. A. Rau**

Pontifical Catholic University of Peru, Lima, Peru

**Patrizia Pereyra**

Pontifical Catholic University of Peru, Lima, Peru

**A. Ruiz**

Instituto Peruano de Prospectores y Desarrolladores, Lima, Peru

## ABSTRACT

The use of mining tailings-based geopolymer binder as a substitute for cement can be an interesting alternative to the problem of final disposing of large volumes of them. Indeed, mining tailings have a high silica content, which makes them suitable for geopolymerization. The tailings samples contain Cu, Pb, Zn, As, Sb, Cd and Bi, mainly. X-ray diffraction results show that the tailings are composed of quartz, SiO<sub>2</sub> (81%). Geopolymerized tailing samples (GTPS) were obtained by varying the ratio of SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> and SiO<sub>2</sub>/NaOH. The compressive strength of the GTPS varied between 2 MPa and 8 MPa. The electrical conductivity in the leaching tests varies between 13.91–16.11 mS/cm<sup>2</sup> indicating that ions are present in the solution. However, the pH = 10.5 indicates that acidity is not being generated. The element that mostly leaches is iron. The highest percentage of leaching is observed for cadmium (69%) and chromium (93%). The concentrations of elements are under the maximum permissible limits for water according to the Peruvian legislation. However, mass transfer leach tests and immersion leach tests must be realized.

## INTRODUCTION

Mining is an important industry in the economy of many countries. For mining operations to develop, the movement of large volumes of material is necessary. In this sense, this

industry generates a variety of solid and semi-solid waste, with tailings being one of the largest volume products generated [1]. In fact, the mining industry generates a huge amount of mine tailings from the excavation of minerals in the form of waste rock from mineral processing [2]. In this sense, it is necessary to implement an adequate management system for the waste generated [3,4].

In recent years, the mining industry around the world has focused its efforts on minimizing this waste, either by reusing it in its operations with the cut-and-fill method [5,6] or looking for alternative uses in society [7]. Another problem with tailings is related to the handling of large volumes that must be disposed of safely [8–10]. One way to reduce or minimize the volume of this waste is to use it as raw material for the production of inputs for other industries [11], such as construction [10, 12–16]. The literature has shown that it is possible to use copper tailings [2,17,18], gold [18–22] and iron [23–30] mixed with geopolymers [18,23,25] as partial Cement substitute for concrete or making construction bricks. In this sense, the use of geopolymerized mine tailings is a new trend of great relevance in the mining industry and especially useful for the reuse of tailings [31–33, 34]. In this article, the preliminary results of obtaining geopolymerized cement from mine tailings are presented.

## **MATERIALS AND METHODS**

### **Collection of Mining Tailings**

The copper-gold mining tailing sample came from a mining operation in northern Peru. The sample containing 25% solids was dried at a temperature around 50°C for 5 days [35]. This tailing was pretreated in order to eliminate the percentage of sulfur [36].

### **Tailing Characterization**

The Inductively Couple Plasma (ICP) analytical method was used to determine the heavy metal concentrations in each sample of liabilities.

### **Mineralogical Tests**

To obtain the mineralogical composition, X-ray diffraction (XRD) was used. The XRD analysis was performed with the DRX Bruker equipment model D8 Discover with copper radiation ( $\text{Cu K}\alpha = 0.15418 \text{ nm}$ ), current of 40 mA and acceleration voltage of 40 kV with a Lynxeye detector with energy selectivity.

The analysis was performed in a range of angles ( $2\theta$ ) from 5 to 80 degrees in steps of 0.02 degrees considering the time per step 1 second. To calculate the composition of the crystalline phases and the amorphous part, the Reference Intensity Ratio (RIR) method was applied [37].

### **X-Ray Fluorescence**

One gram of material was selected for each sample, X-ray fluorescence analyses. X-ray fluorescence analyzes were performed with the Bruker S8 TIGER wavelength dispersive with opening angle of 0.23° and 0.46°. In addition to analyzer crystals: PET, LIF (200), LIF (220) and XS-55, and two types of detectors: scintillation counter and proportional flow. The evaluation model was for oxides and the measurement time was ~17 minutes.

### **Chemical Speciation**

The concentrations of heavy metals in the tailing were determined using Inductive Couple Plasma (ICP) method. To determine the concentrations of metals in the leaching tests, the Atomic Absorption Spectroscopy (AAS) technique was used [38].

### **Acid Base Accounting (ABA) analysis**

The acid mine drainage (DAM) prediction analyzes were carried out following the procedure proposed by Skousen [39]. Then, a sample of 2.0 g of pulverized sample were placed into 250 mL conical flask and 90 mL of distilled water was added. At the beginning of the test, between 1–3 ml of standardized 1,0 N HCl was added. Then the flask

was placed on a shaking apparatus. After 2 hours, a second acid quantity was added. After 24 hours, distilled water was added to bring a volume of 125 mL approximately. Then, the pH was registered before start the neutralization up to 8.3 by adding a standardized solution of 0,5 N or 0,1 N NaOH.

### **Radiometric Analysis**

The radiometric analysis was carried out using gamma-ray spectrometry with a 3x3" NaI(Tl) scintillation detector to determine the activity concentrations (AC) of natural radionuclides. The tailing samples were placed in cylindrical hermetic containers to prevent radon leakage and stored for a period of 28 days to reach secular equilibrium [40].

Quantifications were carried out by the efficiency transfer method using the software ETNA and the standard reference materials IAEA-412 and IAEA-465 with known activities of 40K, 226Ra and 232Th. The 1460 keV, 1764.5 keV and 2614.7 keV gamma lines were used for estimating ACs of 40K, 214Bi(226Ra), and 208Tl(232Th), respectively [41,42].

### **Geopolymerization Process**

For geopolymerization to be carried out, it will be necessary to adjust the molar ratio of Si/Al and Si/Na. In this case, the Si/Al ratio was fixed at 1 and 5 by adding aluminum oxide to the mixture. In the case of the Si/Na ratio, this was set between 0.5 and 2.5. The concentration of sodium hydroxide used in the alkaline solution was set from 9 to 13 molar.

Six geopolymer recipes were prepared by varying the ratios of Si/Al and Si/Na. All recipes were molded in cubic molds of 5cm based on the ASTM C109 standard [43]. After molding, the geopolymers were cured at ambient temperature for 15 days. After this period, the geopolymers were further cured in a furnace at a temperature of 75°C for 7 weeks.

### **Geomechanical Tests**

The standard method provides a means of determining the compressive strength of hydraulic cement and other mortars and results may be used to determine compliance with specifications [43].

### **Leaching Tests**

The tailings samples were mixed with the geopolymers to obtain cubic bricks of five centimeters in measurement. These bricks were subjected to leaching tests in order to identify the metals that could leach after obtaining the geopolymerized cement [44].

In addition, this will allow evaluating if the geopolymerized cement will have an acidity-generating potential, thus complementing the ABA tests.

## RESULTS AND DISCUSSION

### Tailing Characterization

#### Mineralogical Tests

The results of X-ray fluorescence and XRD analysis of the mine tailing sample R5 are presented in Table 1 and Figure 1, respectively. The results show that the sample is predominantly composed of Quartz ( $\text{SiO}_2$ ), with varying concentrations of other minerals such as Muscovite ( $\text{KAl}_2(\text{AlSi}_3\text{O}_{11})(\text{OH})_2$ ), Wollastonite ( $\text{CaSiO}_3$ ) and Caolinite ( $(\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_4)$ ). The mineral phases identified in the sample are of particular interest due to the aluminosilicates compounds for making geopolymer cement based on tailings.

#### Chemical Analysis

The results of the chemical analysis of the tailing sample (R5) using ICP-MS are shown in Table 2. The results show that the sample contains varying concentrations of several elements, including Cu, Cr, Mn, Pb and Zn.


**Table 1. Mineral composition of sample R5**

Crystalline phase	Formula	Concentration (%)
Quartz	$\text{SiO}_2$	81
Muscovite	$\text{KAl}_2(\text{AlSi}_3\text{O}_{11})(\text{OH})_2$	2.7
Wollastonite	$\text{CaSiO}_3$	1.5
Caolinite	$\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_4$	1.0
Hematite	$\text{Fe}_2\text{O}_3$	0.7
Rutile	$\text{TiO}_2$	0.4
Trace elements	Amorphous	12.7

**Table 2. Chemical composition obtained by ICP-MS<sup>1</sup>**

Ag	Al	As	Ba	Be	Bi	Ca	Cd	Co	Cr
ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm
0.3	2.99	6	166	<0.5	<5	0.43	1	6	323
Cu	Fe	Ga	K	La	Li	Mg	Mn	Mo	Na
ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	%
448.4	6.03	19	1.61	4.5	5	0.29	259	16	0.2
Nb	Ni	P	Pb	S	Sb	Sc	Sn	Sr	Ti
ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	%
1	7	0.04	24	1.08	5	2.7	<10	69.3	0.08
Tl	V	W	Y	Zn	Zr	S <sub>total</sub>	S	SO <sub>4</sub> <sup>2-</sup>	Hg
ppm	ppm	ppm	ppm	ppm	ppm	%	%	%	ppm
<2	56	<10	2.2	96.7	10.7	1.1	0.87	0.23	0.01

<sup>1</sup>Analysis performed at SGS laboratory

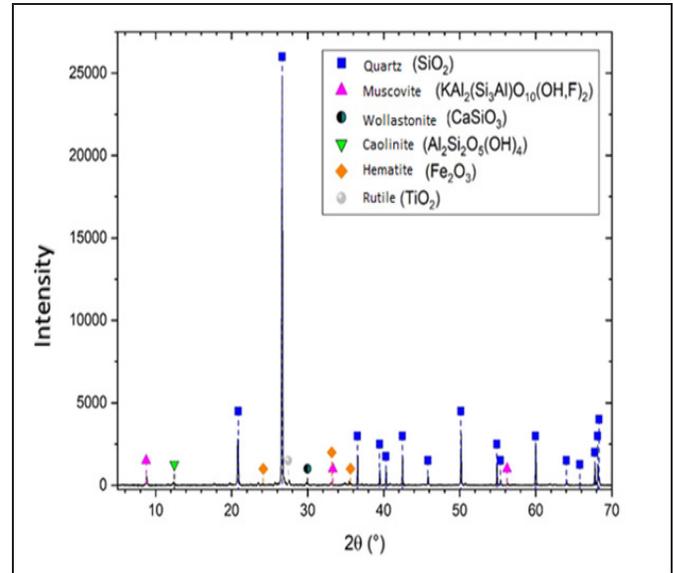

**Figure 1. XRD spectrum of tailing sample (R5)**

#### Radiometric Analysis

Activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  measured in the tailing sample together with the statistical error are given in Table 3.

#### Geopolymerization Process

Geopolymerized tailing samples with different proportions of  $\text{SiO}_2/\text{Al}_2\text{O}_3$  and  $\text{SiO}_2/\text{NaOH}$  varying from 1 to 5; and 1 to 2 respectively were obtained [45]. The samples were

**Table 3. Activity concentration ( $\text{Bq}\cdot\text{Kg}^{-1}$ ) of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in tailing samples**

Sample	AC <sub>40K</sub>	AC <sub>226Ra</sub>	AC <sub>232Th</sub>
R5	$752.4 \pm 35.7$	$9.9 \pm 0.5$	$11.9 \pm 0.6$

**Table 4. Results of geomechanical tests of geopolymerized tailings samples**

Sample	SiO <sub>2</sub> /Al <sub>2</sub> O <sub>3</sub>	SiO <sub>2</sub> /NaOH	Simple Compressive strength (MPa)
RR5-R1	0.95	1.52	6.40
RR5-R2	1.98	1.46	3.87
RR5-R3	3.07	1.50	5.19
RR5-R4	4.29	1.47	5.23
RR5-R5	5.54	1.49	4.06
RR5-R6	2.90	0.47	2.00
RR5-R7	3.13	0.96	2.50
RR5-R8	3.17	1.45	4.94
RR5-R9	3.12	1.90	7.29

obtained by mixing the respective reagents and the pretreated R5 tailing. The proportions used are presented in Table 4.

### Geomechanical Tests

The results of the simple resistance test of geopolymer specimens are shown in Figure 2 and Table 4. The results indicate that the compressive strength of geopolymer samples varies from 2 MPa to 8 MPa. The Greater resistance was achieved in the samples with a ratio SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> of 3.12 and a SiO<sub>2</sub>/NaOH ratio of 1.90, while the lowest resistance

was observed in the samples with a SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> of 2.90 and a SiO<sub>2</sub>/NaOH ratio of 0.47 [45].

According to the Peruvian technical standard [46], type 1 and type 2 bricks must meet the minimum compression resistance of 4.9 and 6.0 MPa. While the value of 2.0 MPa is the minimum required for blocks used in non-load-bearing wall construction.


### Acid Base Accounting (ABA) Analysis

The results of the ABA test are summarized in Table 5. According to the Net Neutralization Potential (NNP) classification criteria [47] and the Neutralization Potential/Acidity Potential (NP/AP) classification criteria [48], only the R5 tailings sample and the pretreated tailings sample (RR5) are potential generators. mine acid drain (DAM).

### Leaching Tests

For leaching tests, only geopolymerized samples that presented a simple resistance test factor greater than or equal to 4.0 were taken into account. The results of the leaching tests are presented in Figure 3 and Table 6. The electrical conductivity in the leaching tests varies between 13.91–16.11 mS/cm<sup>2</sup> indicating that ions are present in the solution.

The pH of the resulting solution is in the basic range for all geopolymerized samples. The concentrations of leached elements are still below the maximum permissible limits for water according to Peruvian legislation [49]. The elements that leach in the greatest quantity are cadmium and chromium with 69% and 93% respectively.

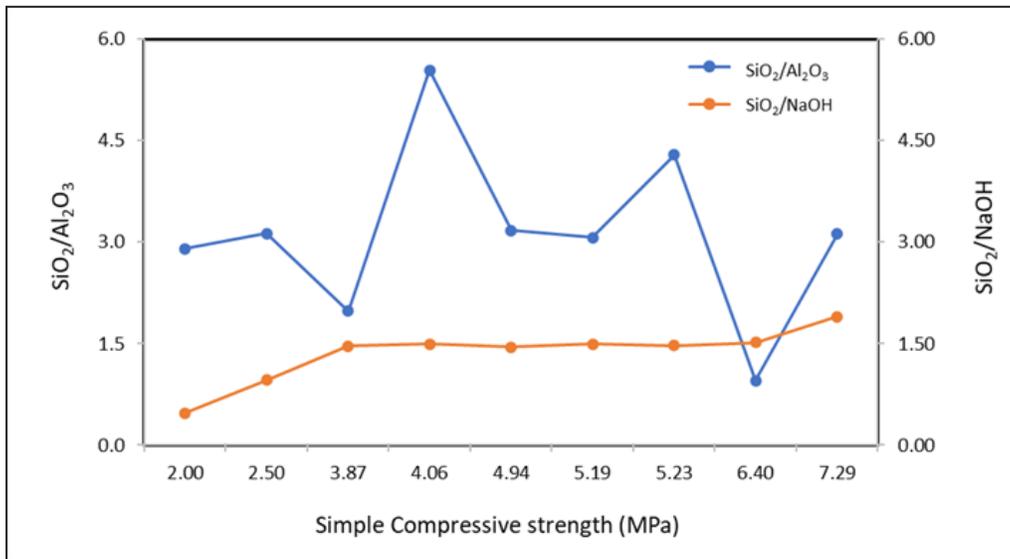


**Figure 2. Variation of simple comprehension tests of geopolymerized samples**

**Table 5. Results of geomechanical tests of geopolymerized tailings samples**

Sample	Acidity potential (AP)	Neutralization potential (NP)	Net neutralization potential (NNP)	NP/AP
R5	27.03	5.47	-21.56	0.20
RR5	17.19	3.94	-13.24	0.23
RR5-R1	4.55	107.24	102.69	23.57
RR5-R2	5.76	87.60	81.84	15.20
RR5-R3	6.32	79.61	73.29	12.60
RR5-R5	6.82	86.68	79.85	12.70
RR5-R8	6.47	86.24	79.76	13.32
RR5-R9	7.28	81.19	73.91	11.16

**Table 6. Results of the leaching tests of the geopolymerized samples**

Sample	Conductivity (uS.cm <sup>-2</sup> )	pH	mg/L					
			Cu	Zn	Fe	Cr	Cd	Pb
RR5	0.19	6.22	0.450	0.010	0.572	0.160	0.004	0.238
RR5-R1	14.86	10.54	0.159	0.079	4.562	0.251	0.039	0.398
RR5-R2	14.41	10.53	0.103	0.056	5.352	0.374	0.041	0.450
RR5-R3	16.11	10.85	0.043	0.030	2.298	0.229	0.052	0.355
RR5-R5	15.03	10.72	0.070	0.019	2.909	0.268	0.046	0.385
RR5-R8	13.91	10.65	0.184	0.053	7.780	0.201	0.043	0.303
RR5-R9	14.60	10.72	0.151	0.093	8.780	0.159	0.049	0.210

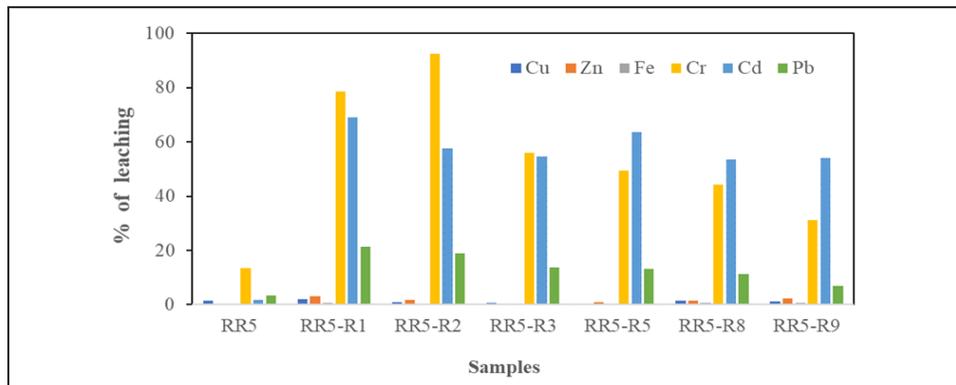

**Figure 3. Comparison of metal leaching percentages in geopolymerized samples**

**Table 7. Metal leaching percentages in the geopolymerized samples**

Sample	% Cu	% Zn	% Fe	% Cr	% Cd	% Pb
RR5	1.5	0.1	0.2	13.5	1.8	3.4
RR5-R1	2.0	3.1	0.5	78.7	68.9	21.3
RR5-R2	1.0	1.7	0.5	92.6	57.6	19.0
RR5-R3	0.6	0.5	0.2	55.9	54.5	13.8
RR5-R5	0.4	0.8	0.2	49.3	63.5	13.1
RR5-R8	1.6	1.5	0.7	44.2	53.4	11.4
RR5-R9	1.2	2.3	0.7	31.1	54.1	7.0

## CONCLUSION

The proportions of  $\text{SiO}_2/\text{Al}_2\text{O}_3$  and  $\text{SiO}_2/\text{NaOH}$  are a key factor for the proper formulation of geopolymerized samples. Results indicate that it is possible to use geopolymerized tailings as raw material for making bricks. Geomechanical tests indicate that it is possible to manufacture type I and type II bricks since the compressive strength results ranged between 2 MPa and 8 MPa. The electrical conductivity values (13.91–16.11 mS/cm<sup>2</sup>) of the leachates from the leaching tests of the geopolymerized samples show a slight leaching of the material. Leaching tests show that bricks do not generate acidic solutions (pH  $\geq$  10.5). The concentrations of the leached elements (Cu, Cd, Zn, Fe, Cr and Pb) of the geopolymerized samples are below the maximum permissible limits despite the fact that the highest leaching percentages are of cadmium (69%) and chromium (93%). These results show that geopolymeric cement made from tailings can be used as a good material for infrastructure with many advantages over conventional cement, such as mechanical resistance, low levels of leached heavy metals, low concentration levels of natural radioactivity with a low degree of radiation contamination.

## Acknowledgment

This work was supported by the Mining Engineering Section and funded by the Pontifical Catholic University of Peru (Grant: E-0015/PI 00752). The authors acknowledge the Center of Materials Analysis of the PUCP (CAM-PUCP) for the facilities to carry out the ICP-MS analyses.

## Competing interest

The authors declare that they have no conflict of interest in the publication.

## REFERENCES

- [1] Carmo, F.F., Lanchotti, A.O., Kamino, L. H.Y. (2020) "Mining Waste Challenges: Environmental Risks of Gigatons of Mud, Dust and Sediment in Megadiverse Regions in Brazil," *Sustainability*, pp. 1–13.
- [2] Nikvar-Hassani, A., Vashaghian, H., Hodges, R., Zhang, L. (2022) "Production of green bricks from low-reactive copper mine tailings: Chemical and mechanical aspects," *Construction and Building Materials*, DOI: 10.1016/j.conbuildmat.2022.126695
- [3] Das, M.R., Satapathy, S., Pothal, L.K. (2023) "A study on waste management in iron mining," *Materialstoday Proceedings*, pp. [doi.org/10.1016/j.matpr.2023.06.368](https://doi.org/10.1016/j.matpr.2023.06.368)
- [4] Kalisz, S., Kibort, K., Mioduska, J., Lieder, M., Malachowska, A. (2022) "Waste management in the mining industry of metals ores, coal, oil and natural gas - A review," *Journal of Environmental Management*, pp.
- [5] Rafaldi, M. J., Seymour, J. B., Richardson, J., Zahl, E., Board, M. (2019) "Cemented Paste Backfill Geomechanics at a Narrow Vein Underhand Cut and Fill Mine," *Rock Mechanics and Rock Engineering*, pp. 4925–4940.
- [6] Hefni, M., Hassani, F. (2020) "Experimental Development of a Novel Mine Backfill Material: Foam Mine Fill," *Minerals*, pp. 1–16.
- [7] Adiguzel, D., Tuylu, S., Eker, H. (2022) "Utilization of tailings in concrete products: A review," *Construction and Building Materials*, pp. 1–10.
- [8] Driussi, C., Jansz, J. (2006) "Technological options for waste minimisation in the mining industry," *Journal of Cleaner Production*, pp. 682–688.
- [9] Rajdeep, D., Ipseet, C. (2013) "Waste management in mining industry," *Indian Journal of Scientific Research*, pp. 139–142.
- [10] Nunar, N., Gautam, A. K. (2019) "Brick Making From Over Burden Dump, a Mine Waste," *International Journal of Scientific Development and Research*, pp. 269–277.
- [11] Tejaswini, M.S.S.R., Pathak, P., Gupta, D.K. (2022) "Sustainable approach for valorization of solid wastes as a secondary resource through urban mining," *Journal of Environmental Management*, pp. [doi.org/10.1016/j.jenvman.2022.115727](https://doi.org/10.1016/j.jenvman.2022.115727)
- [12] Lam, E. J., Zetola, V., Ramírez, Y., Montofré, I. L., Pereira, F. (2020) "Making Paving Stones from Copper Mine Tailings as Aggregates," *Int. J. Environ. Res. Public Health*, 17, 2448. doi:10.3390/ijerph17072448
- [13] Wang, W., Gan, Y., Kang, X. (2021) "Synthesis and characterization of sustainable eco-friendly unburned bricks from slate tailings," *Journal of Materials Research and Technology*, pp. 1697–1708.
- [14] Méndez, D., Guzmán-Martínez, F., Acosta, M., Collahuazo, L., Ibarra, D.; Lalangui, L., Jiménez-Oyola, S. (2022) "Use of Tailings as a Substitute for Sand in Concrete Blocks Production: Gravimetric Mining Wastes as a Case Study," *Sustainability*, 14, 16285. [doi.org/10.3390/su142316285](https://doi.org/10.3390/su142316285)
- [15] Thejas, H.K.; Hossiney, N. (2022) "A short review on environmental impacts and application of iron ore tailings in development of sustainable eco-friendly bricks," *Materialstoday Proceedings*, pp. 327–331.
- [16] Veiga, F., Chambart, H., Vandemeulebroeke, L., Nielsen, P., Adrianto, L. R., Pfister, S., Cappuyns,

- V. (2022) "Mine waste as a sustainable resource for facing bricks," *Journal of Cleaner Production*, 368, 133118. [doi.org/10.1016/j.jclepro.2022.133118](https://doi.org/10.1016/j.jclepro.2022.133118)
- [17] Ahmari, S., Zhang, L. (2012) "Production of eco-friendly bricks from copper mine tailing through geopolymerization," *Construction and Building Materials*, pp. 323–331,
- [18] Gitari, M. W., Akinyemi, S.A., Thobakgale, R., Ngoejana, P.C., Ramugondo, L., Matidza, M., Mhlongo, S.E., Dacosta, F.A., Nemapate, N. (2018) "Physicochemical and Mineralogical Characterization of Musina Mine Copper and New Union Gold Mine Tailings: Implications for Fabrication of Beneficial Geopolymeric Construction Materials," *Journal of African Earth Sciences*, pp. 218–228.
- [19] Roy, S., Adhikari, G. R. (2007) "Use of gold mill tailings in making bricks: A feasibility study," *Waste Management & Research*, pp. 475–482.
- [20] Valdez, J., Aguilar, J., Sanchez, L. (2020) "Diseño e implementación de un proceso alternativo para la fabricación de ladrillos a partir de relaves mineros de Oro," *Ingeniare. Rev. Chil. Ing.*, pp. 268–276.
- [21] Benahsina, A., Taha, Y., Bouachera, R., Elomari, M., Bennouna, M.A. (2021) "Manufacture and Characterization of Fired Bricks from Gold Mine Waste Rocks," *Minerals*, 11, 695. [doi.org/10.3390/min11070695](https://doi.org/10.3390/min11070695)
- [22] Wei, Z., Zhao, J., Wang, W., Yang, Y., Zhuang, S., Lu, T., Hou, Z. (2021) "Utilizing gold mine tailings to produce sintered bricks," *Construction and Building Materials*. 282, 122655. [doi.org/10.1016/j.conbuildmat.2021.122655](https://doi.org/10.1016/j.conbuildmat.2021.122655)
- [23] Kuranchie, F. A., Shukla, S. K., Habibi, D. (2016) "Utilisation of iron ore mine tailings for the production of geopolymer bricks," *International Journal of Mining, Reclamation and Environment*, pp. 1–24.
- [24] Li, R., Zhou, Y., Li, C., Li, S., Huang, Z. (2019) "Recycling of industrial waste iron tailings in porous bricks with low thermal conductivity," *Construction and Building Materials*, pp. 43–50.
- [25] Kumar, R., Das, P., Beulah, M., Arjun, H.R. (2020) "Geopolymer Bricks Using Iron Ore Tailings, Slag Sand, Ground Granular Blast Furnace Slag and Fly Ash. in: Alshaaer, M., Jeon, H. Y. (Eds.), *Geopolymers and Other Geosynthetics*. IntechOpen, London. DOI: 10.5772/intechopen.81748
- [26] Beulah, M., Sudhir, M. R., Mohan, M. K., Gayathri, G., Jain, D. (2021) "Mine Waste-Based Next Generation Bricks: A Case Study of Iron Ore Tailings, Red Mud and GGBS Utilization in Bricks," *Advances in Materials Science and Engineering*, pp. 1–10.
- [27] Zhang, N., Tang, B., Liu, X. (2021) "Cementitious activity of iron ore tailing and its utilization in cementitious materials, bricks and concrete," *Construction and Building Materials*, 288, 123022, [doi.org/10.1016/j.conbuildmat.2021.123022](https://doi.org/10.1016/j.conbuildmat.2021.123022)
- [28] Thejas, H.K.; Hossiney, N. (2022) "A short review on environmental impacts and application of iron ore tailings in development of sustainable eco-friendly bricks," *Materialstoday Proceedings*, pp. 327–331.
- [29] Thejas H.K., Hossiney, N. (2022) "Alkali-activated bricks made with mining waste iron ore tailings," *Case Studies in Construction Materials*, 16, e00973. [doi.org/10.1016/j.cscm.2022.e00973](https://doi.org/10.1016/j.cscm.2022.e00973)
- [30] Thejas H.K., Hossiney, N. (2022) "Compressed unfired blocks made with iron ore tailings and slag," *Cogent Engineering*, 9 (1), 2032975. DOI: 10.1080/23311916.2022.2032975
- [31] Xiaolong, Z., Shiyu, Z., Hui, L., Yingliang, Z. (2021) "Disposal of mine tailings via geopolymerization," *Journal of Cleaner Production*, pp. 1–15.
- [32] He, X., Yuhua, Z., Qaidi, S., Isleem, H. F., Zaid, O., Althoey, F., Ahmad, J. (2022) "Mine tailings-based geopolymers: A comprehensive review," *Ceramics International*, pp. 24192–24212.
- [33] Krishna, R.S., Shaikh, F., Mishra, J., Lazorenko, G., Kasprzhitskii, A. (2021) "Mine tailings-based geopolymers: Properties, applications and industrial prospects," *Ceramics International*, pp. 17826–17843.
- [34] Rao, F., Liu, Q. (2015) "Geopolymerization and Its Potential Application in Mine Tailings Consolidation: A Review," *Mineral Processing and Extractive Metallurgy Review*, pp. 399–409.
- [35] Cook, E.M., DuMont, D. (1991) *Process Drying Practice*, McGraw-Hill, New York.
- [36] Nakhaei, F., Irannajad, M. (2017) "Sulphur removal of iron ore tailings by flotation," *Journal of Dispersion Science and Technology*, pp. 1755–1763.
- [37] Zanko, L. M., Niles, H. B., Oreskovich, J. A. (2008) "Mineralogical and microscopic evaluation of coarse taconite tailings from Minnesota taconite operations," *Regulatory Toxicology and Pharmacology*, pp. S51–S65.
- [38] Hidalgo, A., Andrade, C., Alonso, C. (2001) "An accelerated Leaching Test to Evaluate the Long-Term Behaviour of Concrete in Waste Disposal," *L'Industria Italiana del Cemento*, pp. 498–507.
- [39] Skousen, J., Simmons, J., McDonald, L.M., Ziemkiewicz, P. (2002) "Acid-base accounting to

- predict post-mining drainage quality on surface mines,” *Journal of Environmental Quality*, pp. 2034–2044.
- [40] Gilmore, G. (2008). *Practical gamma-ray spectroscopy*. John Wiley & Sons, Warrington.
- [41] ASTM. (2020) Standard Practice for the Rapid Assessment of Gamma-ray Emitting Radionuclides in Environmental Media by Gamma Spectrometry. D7784 – 20.
- [42] Liza, R., Pereyra, P., Rau, J., Guzman, M., Sajo-Bohus, L., Palacios, D. (2023) “Assessment of Natural Radioactivity and Radon Exhalation in Peruvian Gold Mine Tailings to Produce a Geopolymer Cement,” *Atmosphere*, pp.1–11.
- [43] ASTM. (2002) Standard Method of Compression Testing 2-inch concrete cubes. C109.
- [44] Van der Sloot, H.A., Van Zomeren, A., Dijkstra, J.J., Hoede, D. (2003) “Prediction of long-term leachate quality and chemical speciation for a predominantly inorganic waste landfill,” *In: Proceedings of the 9th International Waste Management and Landfill Symposium*, pp. 1–12.
- [45] Rau, J., Guzman, M., Pereyra, P., Ruiz, A. (2023) “Recycling of mining tailings in construction materials such as geopolymer cement,” *In: Proceedings of the 21st LACCEI International Multi-Conference for Engineering, Education, and Technology*, Buenos Aires, pp. 15–30.
- [46] INDECOPI. (2002) Peruvian technical standard. Masonry units. Concrete blocks for structural use. Requirements. [In Spanish]. NTP 399.602.
- [47] Lapakko, K. (1994) “Evaluation of neutralization potential determinations for metal mine waste and a proposed alternative,” *Journal of the American Society of Mining and Reclamation*, pp. 129–137.
- [48] Price, W.A., Morin, K., Hutt, N. (1997) “Guidelines for the prediction of acid-rock drainage and metal leaching for mines in British Columbia: part II recommended procedures for static and kinetic testing,” *In: Proceedings of the 4th international conference on acid rock drainage*, Vancouver, pp. 15–30.
- [49] MINAM. (2010) Peruvian Maximum Permissible Limits for Liquid Effluent of Mining and Metallurgical Activities. [in Spanish]. D.S. N° 010-2010-MINAM.

# Geosensing for Exploration—New Technology for Underground Directional Drilling

## Scott Thomson

CoalBed Innovations, Lake Macquarie, NSW  
Australia

## Duncan Thomson

CoalBed Innovations, Lake Macquarie, NSW  
Australia

## Dan Brunner

REI Drilling, Inc, Salt Lake City, UT

## Ben Lyddall

REI Drilling, Inc, Salt Lake City, UT

## ABSTRACT

Geosensing is used in oilfield drilling in conjunction with geophysical tools to support characterization of rock properties, geology, and reservoir conditions. This technology is now available to the mining industry and has been successfully applied to underground in-seam directional drilling in Australian coal mines for geologic exploration and methane drainage. The system utilizes a range of drill rig and wellhead mounted sensors which, combined with analytical software, produce real-time data from which 3D spatial features can be accurately modelled significantly in advance of mining. This innovation greatly expands on the information obtained from current in-seam directional drilling practices and provides for improved characterization of coal seams, including soft and weak zones, locations of geologic discontinuities, and analysis of formation flow.

This paper provides a description of the geosensing system and the interpretation of actual data from long in-seam directionally drilled methane drainage boreholes at mines in Australia, and discusses how this system increases the value of directional drilling as an exploration tool for the coal mining sector, and the evaporite and hard-rock mining sectors where directional drilling is also applied.

## INTRODUCTION

### Background

Underground in-seam directional drilling is performed extensively in Australian coal mines as the primary tool for

methane drainage in gassy mines. Although effective for methane drainage, in-seam directional drilling also creates an opportunity to record valuable geological data, which has not been effectively realized due to limitations in existing underground in-seam directional drilling technology.

Historically, underground in-seam directional drilling has been performed with methane drainage in mind, and not subsurface exploration. Geological uncertainty remains the bane of many high-capacity underground coal operations. There are many examples in which large geological structures (such as faults, intrusions, etc.) or smaller outburst-prone features have been missed by in-seam drilling programs, only to be subsequently intercepted by continuous miners or longwalls. This has serious safety and productivity implications and severely limits the development of mining automation technologies without greater certainty in geological interpretation in advance of the face.

Currently, these issues exist at many operations due to ambiguous interpretations of surface-based geophysical data; and the lack of certainty in data generated by surface exploration drilling and underground in-seam directional drilling programs, the latter of which are entirely reliant on the driller's logs of "hard, soft, grey returns, coal/shale mix" or similar. Standards of reporting vary, and misinterpretation is common.

New developments in geosensing technology involve placing a series of real-time sensors onto existing underground directional drilling rigs, which integrate this data flow into the drilling process via interpretative software.